

COMBUSTION DERIVED ULTRAFINE γ -Fe₂O₃ Structure, morphology and thermal studies

*N. N. Mallikarjuna, B. Govindaraj, Arunkumar Lagashetty and
A. Venkataraman**

Department of Chemistry, Gulbarga University, Gulbarga-585 106, India

Abstract

A novel combustion method of employing poly(ethylene glycol) with the precursor in a fixed ratio for the synthesis of ultrafine γ -Fe₂O₃ through a self-propagating combustion synthesis is reported. Four different precursors viz. ferrous hydroxide, ferrous oxalate dihydrate, ferric 8-hydroxyquinoline and ferric acetylacetonate are employed in this study for the conversion of these precursors to ultrafine γ -Fe₂O₃ particles. The as synthesized γ -Fe₂O₃ samples are characterized by XRD, SEM and thermal techniques. A case study for the synthesis of γ -Fe₂O₃ employing ferric acetylacetonate as precursor is reported. The importance of employing thermal analysis techniques in understanding the combustion synthesis is envisaged.

Keywords: poly(ethylene glycol), precursors, self-propagating combustion reaction, thermal and structural studies, ultrafine γ -Fe₂O₃

Introduction

Maghemite has attracted technological interest due to its magnetic and catalytic properties. Interest has increased following the observation that the properties are strongly dependent on the size of particles with dramatic changes when ultrafine/nanometric sizes are acquired [1–6]. The new synthetic routes for the preparation of ultrafine γ -Fe₂O₃ are under constant investigation and some of them include the ion-exchange reaction in α -NaFeO₂ with benzoic acid [7], co-precipitation [8], thermal decomposition of metal hydrazine complexes [9], through a wet chemical synthesis of successive hydrolysis, oxidation and dehydration of ferrous chloride to obtain as small as 5 nm particles [10], selective oxidation of Fe²⁺ and Fe³⁺ [11], thermal decomposition of lipodocracite from solid solutions [12], thermal decomposition of metal carboxylate under the controlled conditions [13], and through ore beneficiation [14]. The porous nanosized iron oxide films prepared by the polymer precursor method using polyvinyl alcohol [15]. Many of these methods involved in the synthesis of γ -Fe₂O₃ are tedious, some of them time consuming with many reaction steps and often in many cases a small quantity of the material could be synthesised. Knowledge of the formation of the final product from its precursors through the use of thermal analysis

* Author for correspondence: E-mail: raman_chem@reddifmail.com.

techniques has gained importance in understanding the synthesis of materials [16–19].

Present investigation is a continuation of new synthetic routes using new precursors for the synthesis of ultrafine monophasic γ -Fe₂O₃. In the present study we have employed four different precursors viz. ferrous hydroxide, ferrous oxalate dihydrate, ferric 8-hydroxyquinoline, ferric acetylacetonate along with polyethylene glycol as an oxidant in a fixed ratio of 1:5 through a self-propagation combustion reaction.

It is reported in literature that poly(vinyl alcohol) can be employed as an oxidizing agent along with urea for the synthesis of other spinel ferrites through the combustion of citrate precursor [20]. However, this technique has some limitations viz., use of urea as a fuel, and also that poly(vinyl alcohol) has a wide variation of molecular masses, both of these parameters would influence the combustion to undergo as a highly exothermic reaction. Hence a new fuel which can also work as a controllable oxidant in a combustible reaction generating self-propagation is essential. In search of a suitable economic oxidant generating a self-propagating reaction, our use of poly(ethylene glycol) has given promising results in case of α -Fe₂O₃ to γ -Fe₂O₃ conversion [21]. In present investigation we report the synthesis of γ -Fe₂O₃ by employing poly(ethylene glycol), which acts as a reducing agent in the initial stage and this is followed with oxidation in the final combustion process. The as synthesized γ -Fe₂O₃ samples are then characterized by employing the thermal, structural, and scanning electron microscopy techniques. The thermal behavior of the combustion process employing ferric acetylacetonate precursor as an example is considered in detail for understanding the possible process and progress of the self-propagating combustion reaction. This thermal study is also undertaken in two different atmospheres viz. dynamic O₂ and N₂ to understand the effect of atmosphere.

Experimental

Poly(ethylene glycol) with molecular mass 4.000 was obtained commercially. All the other chemicals employed were AR grade.

Preparation

The precursors ferrous hydroxide, ferrous oxalate dihydrate, ferric 8-hydroxyquinoline and ferric acetylacetonate were prepared as reported elsewhere [23]. The above four precursors were mixed with poly(ethylene glycol) in the mass ratio 1:5 and ground together in a mortar. The resultant solids were placed in a silica crucible and heated in the air using a Bunsen burner. It was observed that poly(ethylene glycol) first melts, forms froths and ignites to form γ -Fe₂O₃ as residue. On cooling the residue to room temperature no traces of carbon impurities were observed. This reaction which occurs with the evolution of lot of gases and ignites autocatalytically is called a strong self-propagating combustion reaction, as it resembles the strong combustion reaction for the preparation of SnO₂ [24]. As this reaction is fast i.e., going to completion within 2–3 min, and ignites autocatalytically, the exact temperature of the

reaction could not be measured. However using a thermocouple the highest temperature of the reaction was found to be around 500°C. Thermal analysis traces for the reaction is explained in the later section. The γ -Fe₂O₃ samples obtained from the precursors viz., ferrous hydroxide ferrous oxalate dihydrate, ferric 8-hydroxy quinoline and ferric acetylacetonate in the present study are henceforth designated as NM₁, NM₂, NM₃ and NM₄ samples respectively.

Characterization

The thermal analysis curves were obtained from the Mettler Toledo Star instrument or polymer laboratories STA/1500 under static air, dynamic O₂ and dynamic dry nitrogen from room temperature to 800°C, with a heating rate of 10°C min⁻¹. The flow rate under the two dynamic atmospheres was 100 mL min⁻¹. The powder X-ray diffraction patterns were obtained from GEOL JDX-8P or SEIMEN (Japan) X-ray diffractometer using CoK_α radiation and the indexing was done by employing PROSZKI program. The morphology of the maghemite (γ -Fe₂O₃) samples were obtained on Leica Cambridge-440 scanning electron microscopy.

Result and discussion

Particle morphology

The particle morphology of γ -Fe₂O₃ samples is shown in Figs 1a–d with the help of scanning electron micrographs. Following observation are made from the SEM images:

Figure 1a shows the SEM image of NM₁ sample. This image shows the interconnected ultrafine γ -Fe₂O₃ particles with nanosized dimensions forming agglomerates. Most of the particles are spherical. The structure of this material shows particles (<0.1 μm) and conchoidal fracture surfaces. The distribution of small particles was irregular but could not have arisen through a nucleation and growth reaction.

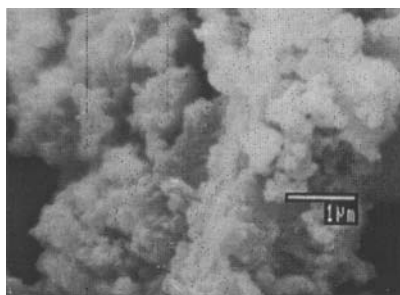


Fig. 1a SEM micrograph of γ -Fe₂O₃ prepared from ferrous hydroxide precursor (NM₁)

Figure 1b shows the SEM image of NM₂ sample. The particles are spherical and joined together to form chains of different dimensions. Joints as necking between the particles are also observed. A few agglomerates of particles of fine γ -Fe₂O₃ with non-chained structure are also observed.

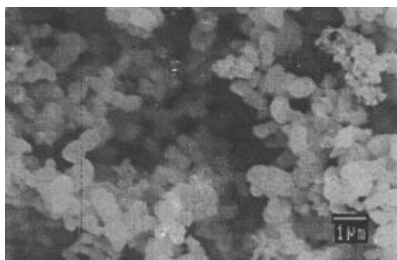


Fig. 1b SEM micrograph of γ -Fe₂O₃ prepared from ferrous oxalate dihydrate precursor (NM₂)

Figure 1ci shows the SEM image of NM₃ sample under low resolution. Ultrafine γ -Fe₂O₃ particles <100 nm, size are observed. In this figure it is also observed a dense and a very closely packed bamboo-like fiber of γ -Fe₂O₃ particles. On closer observation under high resolution (1 μ m) shown in Fig. 1cii, some cracks are seen on the surface of this bamboo-like fiber, which might have resulted from the internal strains developed by the excess gases liberated during the combustion process. This bamboo-like structure indicates a self-assembly of nanosized γ -Fe₂O₃ particles. The bamboo-like fiber observed in here is similar to the MgO fiber reported elsewhere [25]. The difference in the present study is that the γ -Fe₂O₃ surface is not smooth when compared with the MgO fiber.

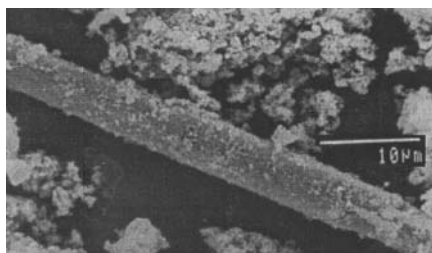


Fig. 1ci SEM micrograph of γ -Fe₂O₃ prepared from ferric 8-hydroxyquinoline precursor (NM₃) (low resolution)

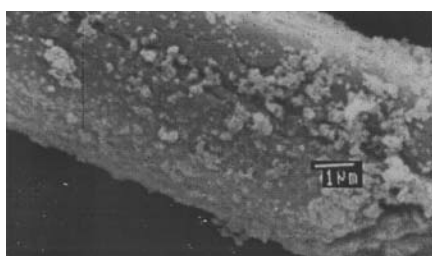


Fig. 1cii SEM micrograph of γ -Fe₂O₃ prepared from ferric 8-hydroxyquinoline precursor (NM₃) (high resolution)

Figure 1d shows the SEM image of NM₄ sample. This image shows very closely knitted continuous chains in three dimensions. On comparison between Fig. 1b, this figure shows a much better image of the particle packing and morphology.

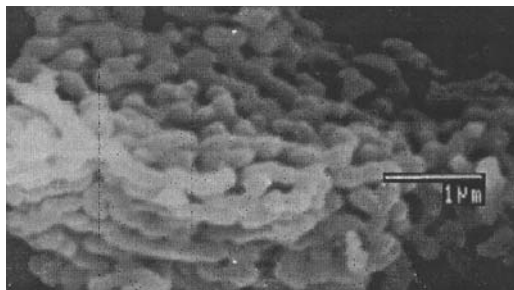


Fig. 1d SEM micrograph of γ -Fe₂O₃ prepared from ferric acetylacetonate precursor (NM₄)

It is observed from the above SEM images, that different precursors under the same experimental conditions for synthesis of γ -Fe₂O₃ gave different particle morphology. Some similarity is observed in NM₂ and NM₄ samples with the presence of chain like structures. However, NM₄ sample shows clear three-dimensional knitting of closed packed γ -Fe₂O₃ particles. The NM₃ sample shows a large bamboo-like fiber, with some surface cracking while the NM₁ sample showed a conchoidal fracture surface. It may be envisaged from these SEM images that the role of precursor is important in deciding the particle morphology of the final product.

On the basis of these SEM images, it is observed that NM₄ sample shows a better particle morphology for its possible application as a heterogeneous catalyst.

From the textural observations in Figs 1a–d, we conclude that comprehensive fusion does not occur. Careful examination of these images revealed no evidence of intracrystalline melting. However in case of sample NM₄ some general indications are that, the reaction preceded by a nucleation and growth process as noticed in any reaction interface, this image has resemblance with the SEM image for the Ni₁C_{0.6} obtained by the thermal decomposition of nickel acetate [26].

It is also observed from literature that understanding the thermal behavior of the reaction path helps in envisaging the particle morphology of the final product [27]. The thermal behaviour of ferric acetylacetonate and the synthesis of γ -Fe₂O₃ from the precursor was carried out as a case study in the light of the above mentioned interesting aspects of NM₄ sample.

Thermal analysis

Figure 2 shows the DTA traces of NM₁, NM₂, NM₃ and NM₄ samples. The traces are taken under a static air atmosphere and the results are tabulated in Table 1. The endothermic peak at 64 and its shoulder at 88°C for NM₁ sample correspond to the loss of absorbed water molecules on the γ -Fe₂O₃ sample in two steps. A strong endothermic peak at 98°C corresponds to the loss of absorbed water molecule for NM₄ sample. It is believed that the storage and liberation of energy with regard to deformation and annealing are the important features in understanding the solid state reactions. The recovery or recrystallisation being the main energy releasing process of deformed solids has been investigated exclusively on metals and calcium carbonates [28]. In this

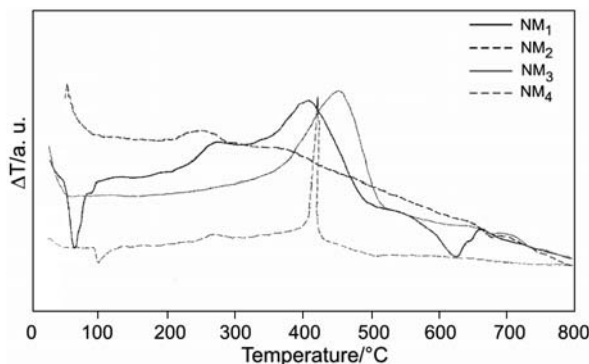


Fig. 2 DTA traces of NM₁, NM₂, NM₃ and NM₄ samples under static air atmosphere

Table 1 Characteristics of DTA traces of as synthesized γ -Fe₂O₃ samples

Sample code	Endothermic peak/°C	Exothermic peak/°C
NM ₁	64(s), 88(sh), 626(w)	269(w), 400(b), 661(w)
NM ₂	657(w)	242(bw)
NM ₃	–	446(vb), 692(w)
NM ₄	98(w)	269(bw), 419(s)

s=strong, w=weak, b=broad, vb=very broad, bw=broad and weak, sh=shoulder

Fig. 2 the exothermic peaks observed at 269°C for NM₁ and NM₄ samples, and the exothermic peak at 269°C for NM₄ sample correspond to the recrystallisation of γ -Fe₂O₃ i.e., a change from cubic to tetragonal crystal system, which is in accordance with the similar observations reported elsewhere [28]. The broad exothermic peak around 400 for NM₁, around 242 for NM₂, 446 for NM₃ and a very sharp peak around 419°C for NM₄ samples correspond to the $\gamma \rightarrow \alpha$ transition (γ -Fe₂O₃ \rightarrow α -Fe₂O₃ transition). This transition was confirmed from the X-ray diffraction patterns of isothermally heated NM₁ and NM₂ samples at 400, and 245 respectively, NM₃ sample at 450 and NM₄ sample at 420°C under a static air atmosphere for two hours each, which showed the α -Fe₂O₃ pattern in each case. The successive endothermic and exothermic peaks at higher temperature i.e., at 627, and 662 for NM₁ and 658 for NM₂ and 693°C for NM₃ samples correspond to the crystal structure changes taking place in the α -Fe₂O₃ samples, as α -Fe₂O₃ is found to exist in different crystal forms (e.g. rhombohedral, hexagonal etc.). However in the NM₄ sample the recrystallisation of α -Fe₂O₃ formed was not prominently observed on the DTA trace.

Now, on comparison of the above DTA traces, the following features are observed:

– Dehydration is observed for NM₁ and NM₄ samples. However, the process of dehydration in these two cases seems to be different, due to the presence of shoulder for the main peak in NM₁ sample.

– The recrystallisation from cubic to tetragonal crystal system is observed for NM₁ and NM₄ and not observed for NM₂ and NM₃ samples.

– Here, $\gamma \rightarrow \alpha$ transition is observed for all the samples and in case of NM₄ sample, this transition is well defined.

– The phase changes of α -Fe₂O₃ is observed for the NM₁, NM₂ and NM₃ samples with the presence of weak exothermic and endothermic peaks. While the phase change was not observed in case of NM₄ sample.

Looking into the above DTA traces, it is strongly felt that the NM₄ sample that shows a well-defined dehydration and $\gamma \rightarrow \alpha$ transition is a suitable example for the case study for the synthesis of γ -Fe₂O₃. It is also a well-known fact that the particle morphology plays an important role on the shapes of the DTA traces. The effect of these variations in shape and size of NM₁ to NM₄ samples as observed in Figs 1a–d have resulted in the changes in the shape index of DTA traces as shown in Fig. 2.

For the synthesis and stabilization of a well-defined γ -Fe₂O₃, the presence of water and along with the particle favourable morphology is found to be essential. NM₄ sample in the present study has a clear dehydration step as noticed from the thermal traces and favorable particle morphology and size as observed on the SEM images. The lower $\gamma \rightarrow \alpha$ -Fe₂O₃ transformation temperature for NM₂ sample and the higher $\gamma \rightarrow \alpha$ -Fe₂O₃ transformation temperature for NM₃ sample might then be due to the absence of water of hydration in the former case and the favorable particle morphology in the later case.

It is important to understand the progress of thermal decomposition of the precursor i.e. ferric acetylacetonate for the study of its decomposed products. It is also essential to understand the thermal behavior of ferric acetylacetonate with poly(ethylene glycol) in the fixed ratio of 1:5 respectively for obtaining γ -Fe₂O₃ (NM₄ sample). This study of mixing ferric acetylacetonate with poly(ethylene glycol) is undertaken under two different atmospheres viz. dynamic O₂ and N₂ to understand the effect of atmosphere and these results are discussed.

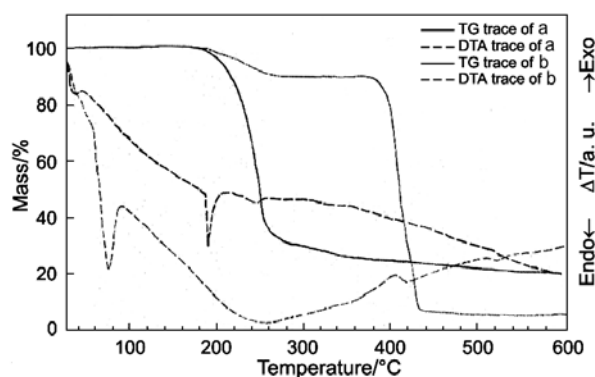


Fig. 3 a – TG/DTA trace of ferric acetyl acetonate under dynamic nitrogen atmosphere.
b – TG/DTA trace of ferric acetyl acetonate + PEG (1:5 mass ratio) under dynamic nitrogen atmosphere

Figure 3a shows the TG/DTA trace for ferric acetylacetonate precursor under dynamic nitrogen atmosphere. The characteristics of TG/DTA traces are given in Table 2. The final mass loss of 80% corresponds to the decomposition of ferric acetylacetonate to form α -Fe₂O₃ as residue. In the Fig. 3a the TG trace shows two stages of mass loss. The first mass loss starts at 175 and ends at 290°C. This stage resembles a sinusoidal curve indicating that the early and later stages of the process have slow rates and correspond to partial decomposition of ferric acetyl-acetonate complex. The second step follows the first step immediately and it is seen as a very slow process starting at 295 and ending at 400°C. The DTA trace shows two endothermic peaks at 199 and 246°C respectively, followed by a very broad and an unending (upto 600°C) endothermic peak.

Table 2 Characteristics of DTA/TG traces of ferric acetylacetonate (FAC) and ferric acetylacetonate+poly(ethylene glycol) (PEG)

Sample	Step	TG T/°C		DTA T/°C	
		start	end	endothermic	exothermic
FAC Under N ₂ atmosphere	I	175	290	199, 246, 600	–
	II	295	400		
FAC+PEG Under N ₂ atmosphere	I	170	278	64, 255, 419	–
	II	280	440		
FAC+PEG Under O ₂ atmosphere		30	330	–	179, 219, 318, 210(sh), 280(sh)

The Fig. 3b shows the TG/DTA trace for ferric acetylacetonate mixed with poly(ethylene glycol) in the ratio 1:5 under dynamic flow of N₂ atmosphere (with the flow rate 100 mL min⁻¹). The TG trace shows a clear two-step mass loss. The first step mass loss starts at 170 and ends at 278°C. The nature of this step resembles the first step mass loss observed for only ferric acetylacetonate shown in the Fig. 3a. However, the mass loss observed here is only 10.5 as compared to 69.5%. The second step of mass loss of 84% is observed as a steady process from 280 to 440°C. Thereafter there is no further decrease in the mass up to 600°C. The DTA trace shows a strong endothermic peak at 64°C and a very broad endothermic peak around 255°C. The third endothermic peak is observed at 419°C. The first endothermic peak at 64°C corresponds to the melting of poly(ethylene glycol). The formation of γ -Fe₂O₃ is completed at 419°C with the presence of third endothermic peak. The TG trace also supports the DTA trace indicating the partial decomposition of ferric acetylacetonate in the first step and a simultaneous decomposition of poly(ethylene glycol) and a partially decomposed ferric acetylacetonate in the second step.

To understand the effect of atmosphere on thermal behavior of the mixture (ferric acetylacetonate+poly(ethylene glycol)), we report the thermal traces under dynamic O₂ atmosphere.

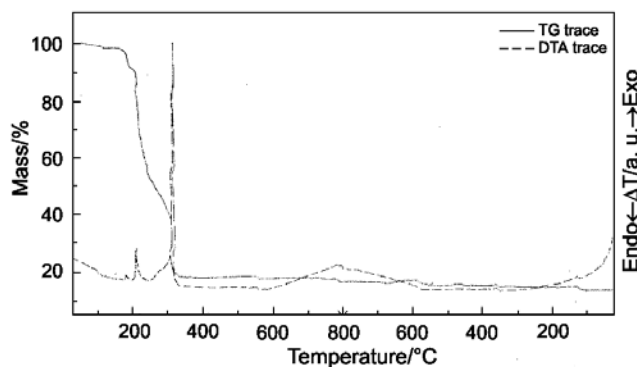


Fig. 3c TG/DTA trace of ferric acetylacetonate+PEG (1:5 mass ratio) on heating and cooling under dynamic O₂ atmosphere

Figure 3c shows the heating and cooling traces for the mixture of ferric acetylacetonate and poly(ethylene glycol) (of mass ratio 1:5) under the dynamic flow of O₂ atmosphere (flow rate 100 mL min⁻¹). TG traces show a complex multistep mass loss starting from the room temperature itself. The mass loss is completed at 330°C. Thereafter the TG trace shows no further loss in the mass upto 60°C and on cooling a slight irregular behavior is seen. The DTA trace shows three main exothermic peaks at 179, 219 and 318°C with shoulders at 210 and 280°C for the peak at 219 and 318°C, respectively. The TG and DTA traces observed here are different when they are compared with the Fig. 3a. The melting of poly(ethylene glycol) is not observed but the exothermic reaction involved in the oxidative decomposition of poly(ethylene glycol) with ferric acetylacetonate is observed along with the presence of these exothermic peaks. The complexities of the DTA trace is supported by the complicated multistep decomposition process in the TG trace. In this regard, it may be understood that the O₂ atmosphere plays a major role by reacting with poly(ethylene glycol) and ferric acetylacetonate mixture. The poly(ethylene glycol) without the aid of dynamic flow of O₂ decomposes the ferric acetylacetonate to obtain predominantly γ -Fe₂O₃ peaks resembling NM₄ sample (Fig. 4d). Hence, the mechanisms under the two atmospheres are different and the final oxide obtained in Fig. 3c is α -Fe₂O₃.

X-ray diffraction

Figures 4a–d shows the XRD pattern of samples NM₁, NM₂, NM₃ and NM₄ respectively. It is observed that all these patterns show cubic crystal system. These XRD data are compared with the ASTM file number 4-0755 for cubic system. The lattice spacing of NM₁, NM₂, NM₃ and NM₄ samples are 8.02, 8.04, 8.21 and 8.30 respectively. In case of NM₁ and NM₂ samples, the lattice spacing is almost same, and in

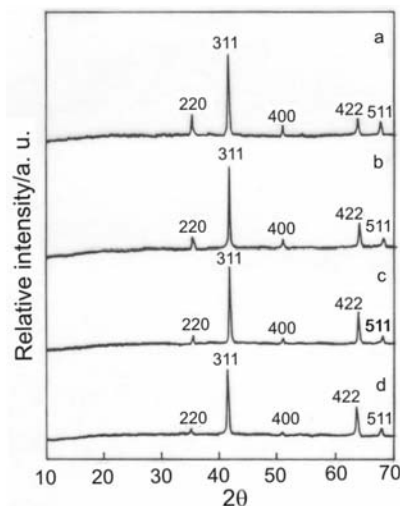


Fig. 4 XRD patterns of NM₁, NM₂, NM₃ and NM₄ samples

NM₃ and NM₄, the values slightly vary. The slight changes in the lattice constant depend upon the history of the sample and precursor used.

Conclusions

The following generalized conclusions may be made from this present study.

The use of poly(ethylene glycol) as a fuel and as a controllable oxidant in the synthesis of ultrafine γ -Fe₂O₃ particles suggests that this combustion route is novel and could be applied for synthesis of other ferrite materials. Also, the synthesis of γ -Fe₂O₃ takes place without going through any of the highly exothermic reactions to achieve ultrafine well-dispersed and high dense γ -Fe₂O₃ particles within a few minutes. However, fixing the proper mass ratio of poly(ethylene glycol) and the precursor is essential for obtaining good quality ultrafine monophasic γ -Fe₂O₃. It is observed from the present study that the particle morphology of the γ -Fe₂O₃ samples is influenced by the precursor taken. Hence, it is possible to tailor-make a given morphology of the final product with proper choice of the precursor. The thermal study (employing TG/DTA techniques) suggests that the phase transition from γ -Fe₂O₃ to α -Fe₂O₃ was also governed by particle morphology. The thermal traces also direct us in understanding the process and possible mechanism of self-propagating combustion reaction in a generalized way.

* * *

The authors are thankful to Prof. C. N. R. Rao President of the Third World Academy of Sciences, JNCASR, Bangalore, for his valuable help and suggestions. N. N. Mallikarjuna, B. Govindaraj and Arunkumar Lagashetty are thankful to the U.G.C., New Delhi for financial support. Thanks are to the Chairman, Department of Chemistry, Gulbarga University, Gulbarga for providing the laboratory facilities.

References

- 1 Q. Li and Y. Wei, *Mater. Res. Bull.*, 33 (1998) 779.
- 2 S. N. Vaidya, *Bull. Mater. Sci.*, 22 (1999) 287.
- 3 R. D. Zysler, D. Fiorani and A. M. Testa, *J. Mag. Mag. Mater.*, 224 (2001) 5.
- 4 R. H. Kodama, *J. Mag. Mag. Mater.*, 200 (1999) 359.
- 5 N. Herron and D. L. Thorn, *Adv. Mater.*, 10 (1998) 1173.
- 6 F. M. Pavel and A. M. Raymond, *Langmuir*, 16 (2000) 8568.
- 7 M. C. Blesa, E. Moran, J. D. Tornero, N. Menendez, E. Mata-Zamora and J. M. Saniger, *J. Mater. Chem.*, 9 (1999) 227.
- 8 M. P. Morales, S. V. Verdaguer, M. I. Montero, C. J. Serna, A. Roig, L. Casas, B. Martinez and F. Sandiumenge, *Chem. Mater.*, 11 (1999) 3058.
- 9 K. Suresh, N. R. S. Kumar and K. C. Patil, *Adv. Mater.*, 3 (1991) 148.
- 10 G. Ennas, G. Marongiu, A. Musinu, A. Falqui, P. Ballirano and C. Caminiti, *J. Mater. Res.*, 14 (1999) 1570.
- 11 N. J. Cherepy, D. B. Liston, J. A. Lovejoy, H. Deng and J. Z. Zhang, *J. Phys. Chem.*, B 102 (1998) 770.
- 12 G. S. Chopra, C. Real, M. D. Alcalá, L. Pérez-Maqueda and J. M. Subtreria, *Chem. Mater.*, 11 (1999) 1128.
- 13 M. M. Rahman and A. Venkataraman, *J. Therm. Anal. Cal.*, 68 (2002) 91.
- 14 K. S. Rane, V. M. S. Vernekar and P. Y. Sawanth, *Bull. Mater. Sci.*, 24 (2001) 331.
- 15 N. Uekawa and K. Kaneko, *J. Phys. Chem. B*, 102 (1998) 8719.
- 16 N. N. Mallikarjuna and A. Venkataraman, *J. Therm. Anal. Cal.*, 68 (2002) 901.
- 17 V. Carles, P. Alphonse, P. Tailhades and A. Rousset, *Thermochim. Acta*, 334 (1999) 107.
- 18 A. Gholinia and F. R. Sale, *J. Thermal Anal.*, 42 (1994) 733.
- 19 N. N. Mallikarjuna, A. Lagashetty and A. Venkataraman, *J. Therm. Anal. Cal.*, (Communicated).
- 20 H. Ochiai and O. Kimura, Preparation of ferrites by the amorphous citrate process. Proceedings of the VIth International Conference on Ferrites (ICF-6), Tokyo and Kyoto, Japan 1992, p. 93.
- 21 A. Venkataraman, V. A. Hiremath, S. K. Date and S. D. Kulkarni, *Bull. Mater. Sci.*, 24 (2001) 101.
- 22 N. N. Mallikarjuna and A. Venkataraman, *Ind. J. Eng. Mat. Sci.*, (Communicated).
- 23 A. I. Vogel, 'Quantitative Inorganic Analysis', ELBS Longman, London 1979.
- 24 L. Fraigi, D. G. Lamas and N. E. Walsoe de Reça, *Nanostruct. Mater.*, 11 (1999) 311.
- 25 G. Kordas, *J. Mater. Chem.*, 10 (2000) 1157.
- 26 A. K. Galwey, S. G. Mackee, T. R. B. Mitchell, M. E. Brown and A. F. Bean, *Reactivity of Solids*, 6 (1988) 173.
- 27 M. E. Brown, R. H. M. Cross, K. C. Sole and M. W. Beck, *Electron microscopy society of South Africa proceedings*, 14 (1984) 153.
- 28 J. Mamoru Senna, *J. Appl. Phys.*, 49 (1978) 4580.